

GUANTE EN ANTICORTE NIVEL 5 RECUBIERTO CON NITRILO SPANDEX

- **Descripción:** Guante en anticorte Nivel 5 recubierto con nitrilo Spandex
- **Marca:** Creator
- **Presentación comercial:** Empaque por par.
- **Fabricación:** Producto Importado

Talla 8 REFERENCIA:C20180238
Talla 9 REFERENCIA:C20180239



Descripción del producto

Guante anticorte nivel 5 recubierto con nitrilo Spandex para proteger de abrasiones moderadas.

Características del producto

- Diseño ergonómico.
- Flexible y fresco
- Excelente agarre en seco y húmedo.
- Libres de costuras que brinda una mayor comodidad y destreza.

Especificaciones del producto

- Hilo hecho a base de Polietileno (AD) de alta densidad y fibra de vidrio.
- Compuesto: Nylon 100 %, Recubierto 100 % Nitrilo.

Aplicaciones

Fabricado para proteger de abrasiones moderadas, donde existan actividades de carga y elementos cortantes, manipulación de piezas, ensamblado, uso de herramientas .



Condiciones de Almacenamiento

- Humedad relativa máxima: 70%
- Temperatura máxima: 32°C
- Almacenar en un lugar fresco y seco, evitando los rayos directos del sol.
- Inadecuadas condiciones de almacenamiento, carga y descarga brutal probablemente afectasen la calidad de los productos.

Disposición Final

- En caso de que el producto se encuentre contaminado con residuos, colóquelo en el respectivo contenedor según cual sea la sustancia o material.
- Los empaques contenedores deberán ser depositada en el contenedor correspondiente a residuos reciclables, en caso que esta se encuentre contaminada por alguna sustancia o material, deséchela en el mismo contenedor donde se depositen estas sustancias

GARANTIA LIMITADA

CREATTOR garantiza que sus productos están libres de defectos en los materiales y en la mano de obra. Un producto sujeto a un reclamo de garantía se debe poner primero a disposición de un distribuidor CREATTOR autorizado o del vendedor a través del cual se ha adquirido el producto.



TEST REPORT

Page 1/4

Report No.: S220602335_1

10 June 2022

Date of receipt : 07 June 2022
Testing period : 09 June 2022
: 09 June 2022

Buyer: —

Sample description: 13G Cut-Resistance Sandy Nitrile Coated Gloves

Test(s) requested : —

Service : REGULAR

Brand / Section : —

Season : —

End use : —

Factory name : —

Factory code : —

Previous report : —

Product category : —

Product type : —

Test stage : FIRST TEST

Supplier name : —

Exported to : —

1. Conclusion:

	Tests description	Conformity
	EN 388:2016+A1:2018	
1	Abrasion resistance: 2016	Level 4
2	Cutting resistance TDM	Level C
3	Tear strength resistance: 2016	Level 4
4	Puncture resistance: 2016	Level 2

Pass: requirements met Fail: requirements not met None: no requirement for this test N/A: not applicable

Approved by



Henry YAN 严滨
Laboratory Manager



TEST REPORT

Page 2/4

Report No.: S220602335_1

10 June 2022

2. Sample(s) description assigned by laboratory:

<u>Size</u>	<u>Analyzed product</u>	<u>Description</u>	<u>Sample information</u>
	GLOVE	palm	



220602335



TEST REPORT


Report No.: S220602335_1

10 June 2022

3. GLOVE/

palm

	Method	Client Requirement	Unit	Result	Conformity
(+) 4.1. Abrasion resistance: 2016 used consumables - abrasive used consumables - adhesive Number of cycles at the hole detection Number of cycles at the hole detection (2) Number of cycles at the hole detection (3) Number of cycles at the hole detection (4) Performance level	EN 388:2016 + A1:2018			Klingspor PL31B Grit 180 3M Scotch >8000 >8000 >8000 >8000 4	
(+) 4.1. Cutting resistance TDM used consumables - blade Coefficient of variation Adjusted factor for blade with neoprene Normalized cutting stroke lengths Normalized cutting stroke lengths (2) Normalized cutting stroke lengths (3) Normalized cutting stroke lengths (4) Normalized cutting stroke lengths (5) Mean normalized cutting stroke length Cut load adjusted for a cut length of 20 mm Level Performance	EN ISO 13997:1999			202200003 % 6.3 0.98 mm 24.4 mm 18.7 mm 16.2 mm 23.5 mm 19.6 mm 20.5 N 11.0 Level C	

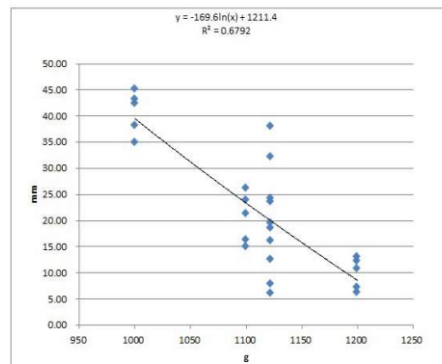

The report is issued by CTC Shanghai under its General Conditions printed overleaf. The results shown in this report refer only to the sample tested. Except by special arrangement, the test items will not be retained by CTC Shanghai for more than 3 months. The test report shall not be reproduced, in full, without the written approval of the testing laboratory.

To declare the conformity to the requirement, the uncertainty of measurement, associated to the test results, has not been taken into account.



TEST REPORT

Report No.: S220602335_1

10 June 2022

	Method	Client Requirement	Unit	Result	Conformity
(+) 4.1. Tear strength resistance: 2016 Tear strength Tear strength (2) Tear strength (3) Tear strength (4) Performance level	EN 388:2016 + A1:2018		N	>75	
			N	>75	
			N	>75	
			N	>75	
				4	
(+) 4.1. Puncture resistance: 2016 Puncture resistance Puncture resistance (2) Puncture resistance (3) Puncture resistance (4) Performance level	EN 388:2016 + A1:2018		N	97	
			N	105	
			N	103	
			N	98	
				2	

END OF TEST REPORT

(+)CNAS accreditation

Unless otherwise specified, the physical test items in this report performed in CTC Shanghai lab were conditioned and tested in the environment of T 23±2°C / RH 50±4%.

Table of Performance Level for Glove

Test Item	Performance Level					
	0##	1	2	3	4	5
Abrasion Resistance (EN 388) Number of cycles (minimum)	<100	100	500	2000	8000	---
Tear Resistance (EN 388) Force (N) (minimum)	<10	10	25	50	75	---
Puncture Resistance (EN 388) Force (N) (minimum)	<20	20	60	100	150	---

Performance level 0 means the glove falls below the minimum performance level for the given individual hazard

Levels of performance for materials tested with EN ISO 13997

	Level A	Level B	Level C	Level D	Level E	Level F
6.3 TDM: cut resistance (N)	2	5	10	15	22	30

The report is issued by CTC Shanghai under its General Conditions printed overleaf. The results shown in this report refer(s) only to the sample tested. Except by special arrangement, the test items will not be retained by CTC Shanghai for more than 3 months. The test report shall not be reproduced, except in full, without the written approval of the testing laboratory.

To declare the conformity to the requirement, the uncertainty of measurement, associated to the test results, has not been taken into account.

